

Barium Fluoride (BaF₂)

Custom sizes and specifications are available

CRYSTALLOGRAPHIC

Syngony	Cubic
Symmetry Class	m3m
Lattice Constants, Angstrom	a=6.196
	c=a
Cleavability	(111), perfect


OPTICAL

Refractive Index at n_e	1.4759
Refractive Index $n_F - n_C$	0.0059
Refractive Index at $n_{10.6}$	1.3926
Refractive Index $n_{8.0} - n_{12.5}$	0.0673
Thermal Coefficient of Refractive Index at 3.39 microns for +/- 60 deg C	(-1.27)... (-1.51) x 10 ⁻⁵
Transmission Range, Microns	0.15 - 12.5
Absorbance $\mu (\lambda), \text{cm}^{-1}$	
at 0.2 microns	0.2
at 0.4 microns	0.08
at 10.6 microns	0.13

THERMAL

Thermal Linear Expansion, deg C ⁻¹ for +/- 60 deg C	(16.5...19.2) x 10 ⁻⁶
Thermal Conductivity, W/(m * deg C) at 38 deg C	7.1
Specific Heat Capacity, J/(kg * deg C)	0.456 x 10 ³
Thermal Stability, deg C	10 +/- 2
Melting Point, deg C	1354

Transmittance $\tau (\lambda)$ vs. Wavelength λ

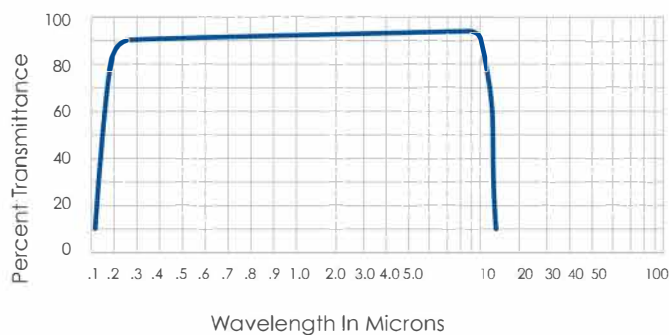

MECHANICAL

Density, g/cm ³ at 20 deg C	4.83
Mohs Hardness	3
Vickers Microhardness, Pa	82 x 10 ⁷
Constants of Elastic Compliance, Pa ⁻¹	$S_{11}=15.30 \times 10^{-12}$ $S_{12}=-4.69 \times 10^{-12}$ $S_{44}=39.47 \times 10^{-12}$
Young Modulus E , Pa	
in <100> direction	6.54 x 10 ¹⁰
in <111> direction	6.63 x 10 ¹⁰
Shear Modulus (G), Pa	
in <100> direction	2.51 x 10 ¹⁰
in <111> direction	2.53 x 10 ¹⁰
Poisson Ratio	0.307

CHEMICAL

Molecular Weight	175.3
Solubility	
in water, gram/100cm ³	0.17
in acids	soluble

Refr. Index n vs. Wavelength λ

WAVELENGTH, MICRONS	REFRACTIVE INDEX
0.2	1.5573
0.5	1.4779
1.0	1.4686
2.0	1.4647
3.0	1.4612
4.0	1.4558
5.0	1.4511
6.0	1.4441
7.0	1.4357
8.0	1.4258
9.0	1.4144
10.0	1.4014
11.0	1.3865
12.0	1.3696
12.5	1.3585
15.0	1.3050

Internal Transmittance $T_i (\lambda)$ vs. Wavelength λ

WAVELENGTH, MICRONS	INTERNAL TRANSMITTANCE
0.2	0.70
0.5	0.96
1.0	0.97
3.0	0.97
5.0	0.97
6.0	0.97
7.0	0.97
8.0	0.97
9.0	0.97
10.0	0.85
12.0	0.42

For Reference Only

ISP Optics Corp:

2603 Challenger Tech Court, Suite 100
Orlando, FL 32826
Tel: +800-909-4207
www.ispoptics.com

ISP Optics Latvia:

24a Ganibu Dambis, korp 13
Riga, LV-1005, Latvia
T: +371 67 323 779
sales@ispoptics.eu



A LightPath COMPANY